

Digital Repository Universitas Jember


Revista de Ingeniería de Construcción

ISSN - 0716 - 2952 versión impresa / print version

ISSN - 0718 - 5073 versión en línea / electronic version



PONTIFICIA UNIVERSIDAD
CATÓLICA DE CHILE
ESCUELA DE INGENIERÍA
DEPARTAMENTO DE INGENIERÍA
Y GESTIÓN DE LA CONSTRUCCIÓN

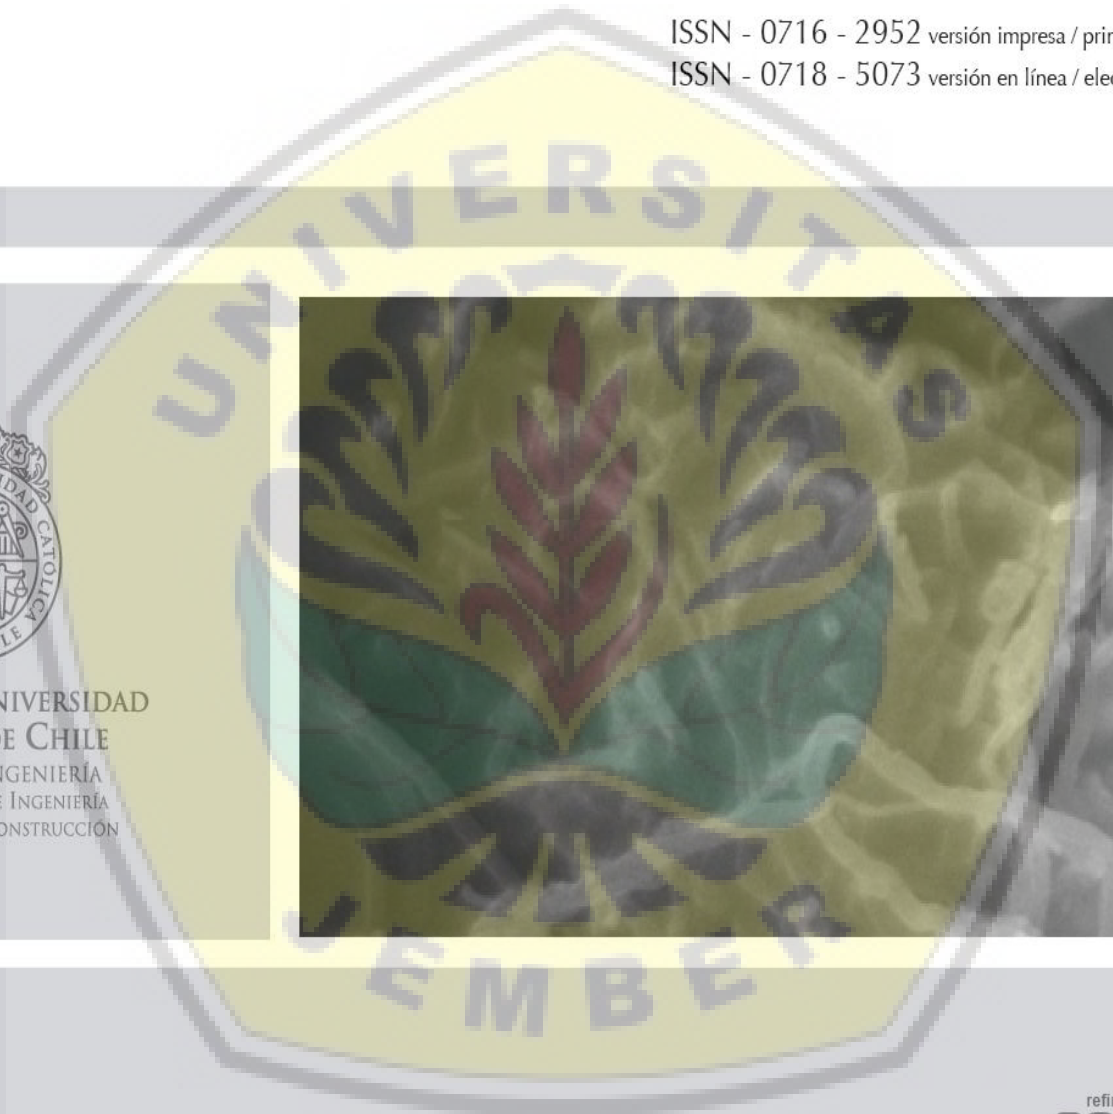

refine your research
SCOPUS

RIC is encouraged by CIB



Scientific Electronic Library Online



Nº3

VOL
35

DICIEMBRE 2020

www.ricuc.cl



HOME

ABOUT


SEARCH

CURRENT

ARCHIVES

ISSN: 0718-5073

Home > Vol 35, No 3 (2020)

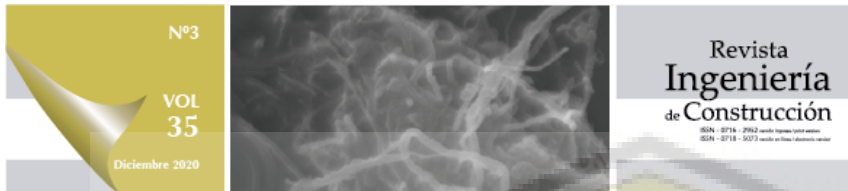

Search Keywords

Search

- Submit a manuscript
- Useful author info
- Login
- Register

Language



Keywords cloud

Brazil Bridges Concrete bridges civil construction
compression strength compressive strength concrete
construction corrosion degradation design
durability energy efficiency evaluation mechanical
properties numerical simulation recycled concrete seismic
vulnerability sustainability water absorption

Vol 35, No 3 (2020)

Table of Contents

Original Research

Practicability in the manufacture of non-structural bricks, from the recycling of cigarette butts

Page 232-245

K. Corredor, Á. Guzmán, N. Torres

▶ Abstract PDF (7MB) PDF (7MB)

Utilizing Industrial Metal Wastes in One-Way Ribbed Reinforced Concrete Panels

Page 246-256

A. Alfeehan, M. Mohammed, M. Jasim, U. Fadehl, F. Habeeb

▶ Abstract PDF (10MB) PDF (10MB)

Calibration of an empirical model for moisture content assessment and monitoring in compacted tropical soils used in the subgrade of road pavements

Page 275-286

I. Pizarro, M. Franço, L. De Almeida, E. Matsura

▶ Abstract PDF (4MB) PDF (4MB)

Comparison addition of rice husk ash and roof tile ash on fly ash-based geopolymer cement with portland cement

Page 287-294

D. Nurtanto, I. Junaidi, W. Wahyuningtyas, W. Yunarni

▶ Abstract PDF (2MB) PDF (2MB)

Lightweight concrete masonry blocks produced with: tire rubber and metakaolin

Page 295-307

C. Fioriti, R. Bravo, J. Melges, J. Akasaki, F. Spósito

▶ Abstract PDF (11MB) PDF (1MB)

Energy efficiency and environmental friendliness, as important principles of sustainability for multifunctional complexes

Page 308-321

O. Zhovkva

▶ Abstract PDF (1MB) PDF (1MB)

Evaluation of the effectiveness of the use of the TDI (Traffic Densification Index) for the prediction of the behavior of nano-modified asphalt mixtures against permanent deformation

Page 322-335

J. Staub de Melo, J. Villena

▶ Abstract PDF (1MB) PDF (1MB)

Experimental Evaluation of Square Ferrocement Panels using Polypropylene Wire Mesh

Page 336-345

Journal Content

- By Issue
- By Author
- By Title

JOURNAL INDEXED AT

- Web of Science ESCI
- Scopus
- Redalyc
- SciELO
- Chemical Abstract
- Periodica
- Latindex
- DOAJ
- RAPRA
- Actualidad Iberoamericana

FOLLOW US

Follow @RIC_UC

Case Study

Comparative seismic analysis of a torsionally-flexible unsymmetric structure by applying NSP, MPA, NLRHA

Page 257-274

C. Medina, D. Galarza





HOME

ABOUT

SEARCH

CURRENT

ARCHIVES

ISSN: 0718-5073

Home > About the Journal > Journal Contact

Mailing Address

Avenida Vicuña Mackenna, #4860 Macul,
Campus San Joaquin, Edificio San Agustín, Piso 3
Casilla 306, correo 22,
Santiago, Chile

Principal Contact

Ximena Araya Gallardo
Departamento de Ingeniería y Gestión de la Construcción Escuela de Ingeniería Pontificia
Unicersidad Católica de Chile
Phone: +56(2)3544488
Email: ric@ing.puc.cl

Support Contact

Revista Ingeniería de Construcción
Phone: +56(2)3544488
Email: ric@ing.puc.cl

Search Keywords

Search

- Submit a manuscript
- Useful author info
- Login
- Register

Language



Keywords cloud

Brazil Bridges Concrete bridges civil construction
 compression strength compressive strength concrete
 construction corrosion degradation design
 durability energy efficiency evaluation mechanical
 properties numerical simulation recycled concrete seismic
 vulnerability sustainability water absorption

Journal Content


- By Issue
- By Author
- By Title

JOURNAL INDEXED AT

- Web of Science ESCI
- Scopus
- Redalyc
- SciELO
- Chemical Abstract
- Periodica
- Latindex
- DOAJ
- RAPRA
- Actualidad Iberoamericana

FOLLOW US

Follow @RIC_UC

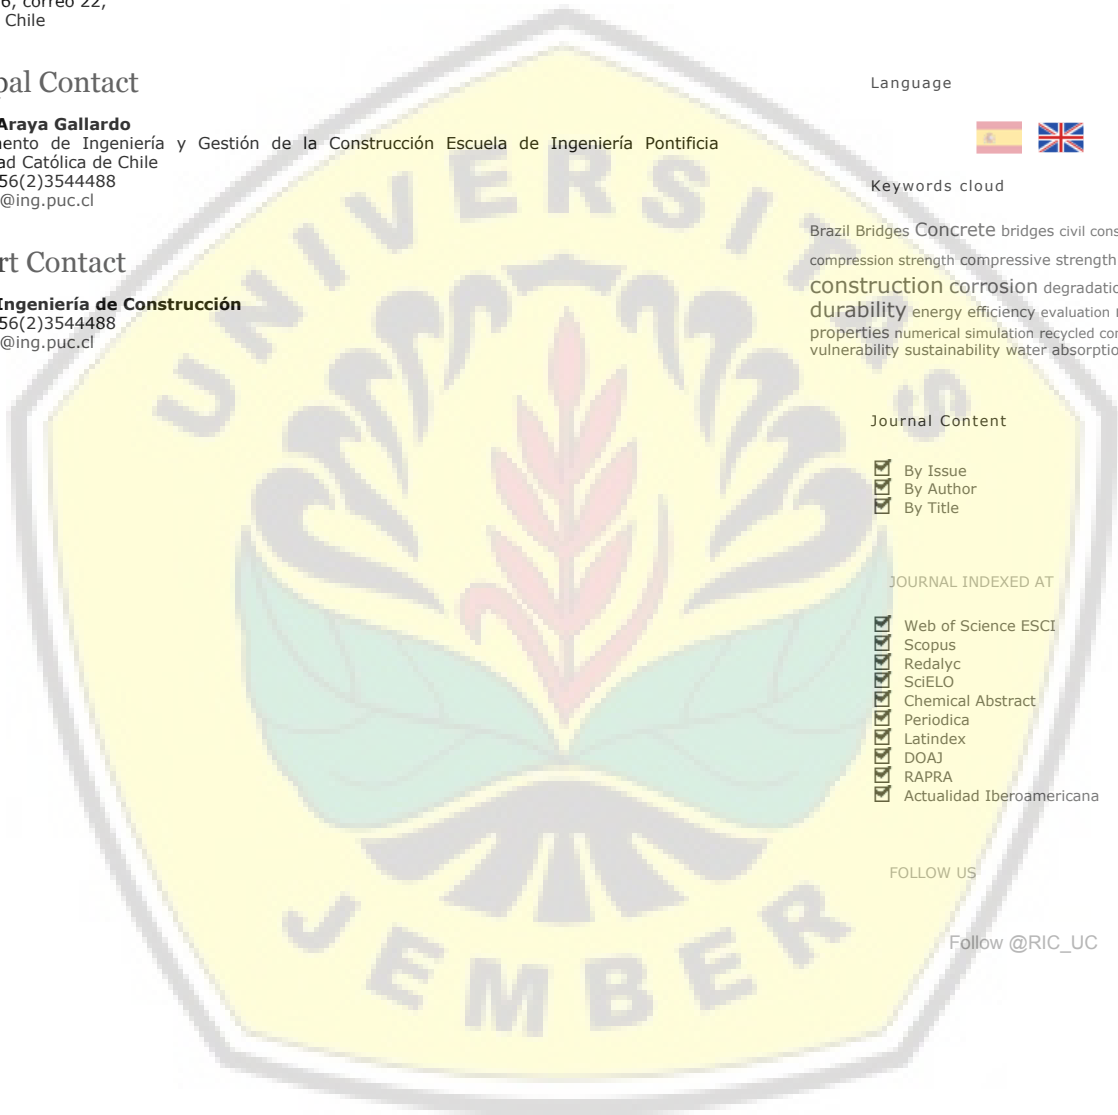



HOME

ABOUT

SEARCH

CURRENT

ARCHIVES

ISSN: 0718-5073

Home > About the Journal > Editorial Team

Coordinator

Ximena Araya Gallardo, Publishing Revista Ingeniería de Construcción, Chile

Search Keywords

Search

- Submit a manuscript
- Useful author info
- Login
- Register

Language



Keywords cloud

Brazil Bridges Concrete bridges civil construction
 compression strength compressive strength concrete
 construction corrosion degradation design
 durability energy efficiency evaluation mechanical
 properties numerical simulation recycled concrete seismic
 vulnerability sustainability water absorption

Journal Content


- By Issue
- By Author
- By Title

JOURNAL INDEXED AT

- Web of Science ESCI
- Scopus
- Redalyc
- SciELO
- Chemical Abstract
- Periodica
- Latindex
- DOAJ
- RAPRA
- Actualidad Iberoamericana

FOLLOW US

Follow @RIC_UC

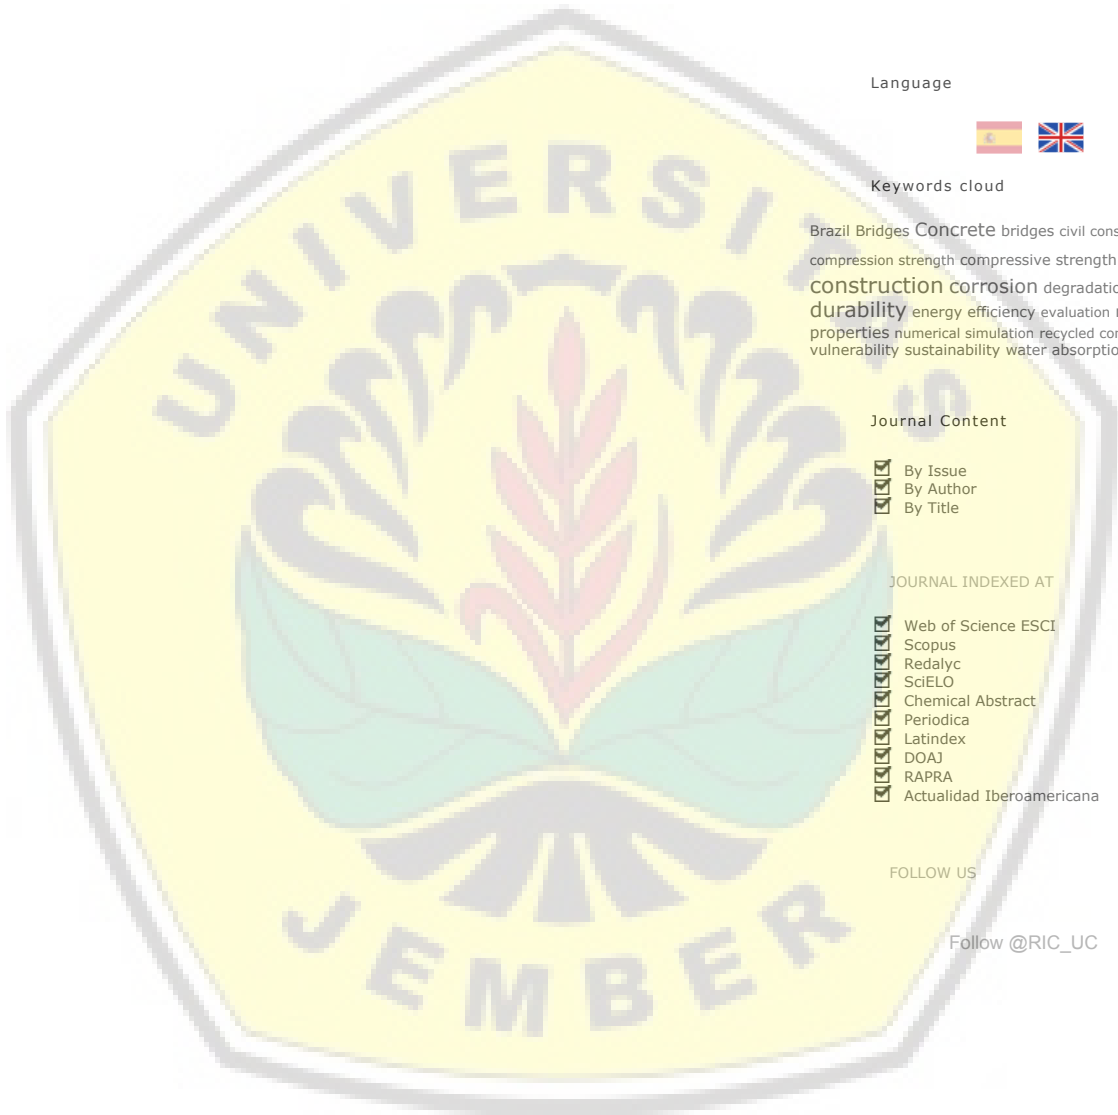



HOME

ABOUT

SEARCH

CURRENT

ARCHIVES

ISSN: 0718-5073

Home > About the Journal > People

Advisory Board

Dr. Alvaro González, Investigador Docente Facultad de Ingeniería Universidad del Desarrollo, Chile

Dr. Marcelo González, Profesor Escuela de Ingeniería UC, Chile

Dr. Pablo Guindos, Pontificia Universidad Católica de Chile, Chile

Dr. Claudio Mourgues, Académico, Escuela de Ingeniería UC

Dra. Alondra Chamorro, Académico, Escuela de Ingeniería UC, Chile

Ph.D. Luis Fernando Alarcón, Professor Escuela de Ingeniería Pontificia Universidad Católica de Chile

Dr. Carlos Videla, Académico, Escuela de Ingeniería UC, Chile

Dr. Sergio Vera, Director Revista Ingeniería de Construcción Director Departamento de Ingeniería y Gestión de la Construcción Escuela de Ingeniería - Pontificia Universidad Católica de Chile

Dr. Hernán de Solminihaç, Académico, Escuela de Ingeniería UC, Chile

Search Keywords

Search

- Submit a manuscript
- Useful author info
- Login
- Register

Language



Keywords cloud

Brazil Bridges Concrete bridges civil construction
 compression strength compressive strength concrete
 construction corrosion degradation design
 durability energy efficiency evaluation mechanical
 properties numerical simulation recycled concrete seismic
 vulnerability sustainability water absorption

Journal Content

- By Issue
- By Author
- By Title

JOURNAL INDEXED AT

- Web of Science ESCI
- Scopus
- Redalyc
- SciELO
- Chemical Abstract
- Periodica
- Latindex
- DOAJ
- RAPRA
- Actualidad Iberoamericana

FOLLOW US

Follow @RIC_UC





HOME

ABOUT

SEARCH

CURRENT

ARCHIVES

ISSN: 0718-5073

Home > About the Journal > People

International Scientific Board

Dr. Jorge Vanegas, Texas A&M University, USA

Dr. Leonardo Rischmoller, Stanford University, USA

Dr. Pedro Castro Borges, Centro de Investigación y Estudios Avanzados del IPN, Mexico

Ph.D. Hans-Dieter Beushausen, University of Cape Town, South Africa

Ph.D. Miquel Casals, Universitat Politècnica de Catalunya, Spain, Spain

Ph.D. Domingo Carreira, Illinois Institute of Technology, USA, United States

Dr. Juan Correall, Universidad de los Andes, Colombia

Dr. Mario Chiorino, Politecnico di Torino, Italy

Ph.D. Alfonso Bastias, Universidad del Desarrollo, Chile

Dr. Leonardo Dueñas, Rice University, USA

Dr. Jorge de Brito, Technical University of Lisboa, Portugal

Dra. Nuria Forcada, Universitat Politècnica de Catalunya, Spain

Dr. Feniosky Pena Mora, University of Illinois at Urbana-Champaign, USA

Dr. Eddy Rojas, The Durham School of Architectural Engineering and Construction University of Nebraska-Lincoln

Dr. Stéphanie Staquet, Université Libre de Bruxelles, Belgium

Dr. Kenji Sakata, Okayama University, Japan

Dr. Sergio Velásquez, Universidad Panamericana, Guadalajara, Mexico

Dra. Patricia Martínez, Universidad de Valparaiso, Chile

Dr. Edgar Muñoz, Pontificia Universidad Javeriana, Colombia

Dr. Jesus de la Garza, Virginia Technological Institute, USA

Dr. Paulo Helene, Univerdad de Sao Paulo, Brasil

Dr. Keith Molenaar, University of Colorado at Boulder, USA

Dr. Paulo Monteiro, University of California at Berkeley, USA

Dr. Martin Fischer, Stanford University, USA

Ph.D. Marcelo Bustos, Uninersidad Nacional de San Juan, Argentina, Argentina

Dr. Vicente González, The University of Auckland, New Zealand

Ph.D. Facundo Almeraya, Grupo de Corrosión del CIMAV, Mexico, Mexico

Search Keywords

Search

- Submit a manuscript
- Useful author info
- Login
- Register

Language



Keywords cloud

Brazil Bridges Concrete bridges civil construction
 compression strength compressive strength concrete
 construction corrosion degradation design
 durability energy efficiency evaluation mechanical
 properties numerical simulation recycled concrete seismic
 vulnerability sustainability water absorption

Journal Content

- By Issue
- By Author
- By Title

JOURNAL INDEXED AT

- Web of Science ESCI
- Scopus
- Redalyc
- SciELO
- Chemical Abstract
- Periodica
- Latindex
- DOAJ
- RAPRA
- Actualidad Iberoamericana

FOLLOW US

Follow @RIC_UC



HOME

ABOUT

SEARCH

CURRENT

ARCHIVES

ISSN: 0718-5073

Home > About the Journal > Editorial Policies

- Focus and Scope
- Section Policies
- Peer Review Process
- Publication Frequency
- Open Access Policy
- Archiving
- Indexes
- Policy of Ethics and malpractice
- Publication charges

Search Keywords

Search

- Submit a manuscript
- Useful author info
- Login
- Register

Focus and Scope

RIC is a journal oriented so much to academics as to professionals. The journal publishes originals and unpublished works, as much in Spanish as in English in all the important topics of engineering and construction management such as: construction materials; technologies, methods and construction processes; construction management and its resources; enterprise management in the construction; viable construction and rehabilitation of materials and structures and other topics of interest. The journal includes articles that inform the results of the investigation as well as applications and practise cases. The opinions expressed in the articles are the sole responsibility of their authors and not necessarily reflect the Engineering Department and Construction Management nor the Publisher point of view. We invite researchers, academics and interested professionals to contribute with articles to be published in the journal or send discussions on the articles already published.

Language



Keywords cloud

Brazil Bridges Concrete bridges civil construction
compression strength compressive strength concrete
construction corrosion degradation design
durability energy efficiency evaluation mechanical
properties numerical simulation recycled concrete seismic
vulnerability sustainability water absorption

Section Policies

Original Research

These items come from original research and have not been previously published, in whole or in part, in another journal. Paper presented in detail, the original results of research projects. Structure generally used contains four parts: introduction, methodology, results and conclusions. Scientific papers will be limited to an area of 5,000 words.

- Open Submissions
- Indexed
- Peer Reviewed

Biography Review

Is defined as work review article whose main purpose is to summarize, analyze and discuss published, related to a single topic. Result of a research paper which analyzes, classifies and integrates research findings published or unpublished, on a field of science or technology, in order to account for the progress and development trends. It is characterized by a careful review of the literature of at least 50 references. Review Articles can not exceed 5,000 words.

- Open Submissions
- Indexed
- Peer Reviewed

Case Study

Case study is a document that presents the results of a study on a particular situation in order to present the technical and methodological experiences given in a specific. Includes an annotated systematic review of the literature on similar cases. He is regarded as a research strategy that includes all the logic design specific approaches to data collection and analysis of data. The Articles of study can not exceed 5,000 words.

- Open Submissions
- Indexed
- Peer Reviewed

Technical Notes

It is work that presents observations and brief scientific descriptions, which are detailed methods and experimental results, however, their introduction and discussion are presented succinctly and in order to locate the study within the scientific context. Technical notes are the way to inform the scientific community about a new method, technique or procedure that is considered of interest to readers of the Journal. Technical notes should not exceed 2,000 words and it will be published in their original language.

- Open Submissions
- Indexed
- Peer Reviewed

Peer Review Process

Peer review: Every article submitted for publication will be reviewed by an internacional comité of referees.

Publication Frequency

Quarterly

The Journal has a Quarterly frequency, the numbers are published on April 30, August 30 and December 30

Journal Content

- By Issue
- By Author
- By Title

JOURNAL INDEXED AT

- Web of Science ESCI
- Scopus
- Redalyc
- SciELO
- Chemical Abstract
- Periodica
- Latindex
- DOAJ
- RAPRA
- Actualidad Iberoamericana

FOLLOW US

Follow @RIC_UC

Open Access Policy

This journal provides immediate open access to its content on the principle that making research freely available to the public, which fosters a greater global exchange of knowledge.

Archiving

This journal has a mirror available at SciELO to ensure secure and permanent preservation of this journal.

Indexes

- Redalyc
 - SciELO
 - Chemical Abstract
 - Periodica
 - Latindex
 - DOAJ
 - RAPRA
 - Actualidad Iberoamericana
-

Policy of Ethics and malpractice


Revista Ingeniería de Construcción ensures ethics and quality of articles, thanks to:

- The final decision of an article is the sole responsibility of the editor, who has the right to review libels, plagiarism, misuse of information, with full freedom to make the necessary inquiries in order to check any wrong practice.
 - All articles submitted for publication are evaluated by an independent committee, this review is blind regarding authors as well as reviewers, only the editor knows the names of those involved.
 - The Journal clearly states in its Guide to Authors, the instructions for publication.
 - The articles must have the author's rights permission in order to be published. The copyright notice must be sent with a signed copy ric@ing.pu.cl
-

Publication charges

This is a fully Open Access journal and and not requires payment of publication fee by the author.

All articles published Open Access will be immediately and permanently free for everyone to read, download, copy, distribute and use online.

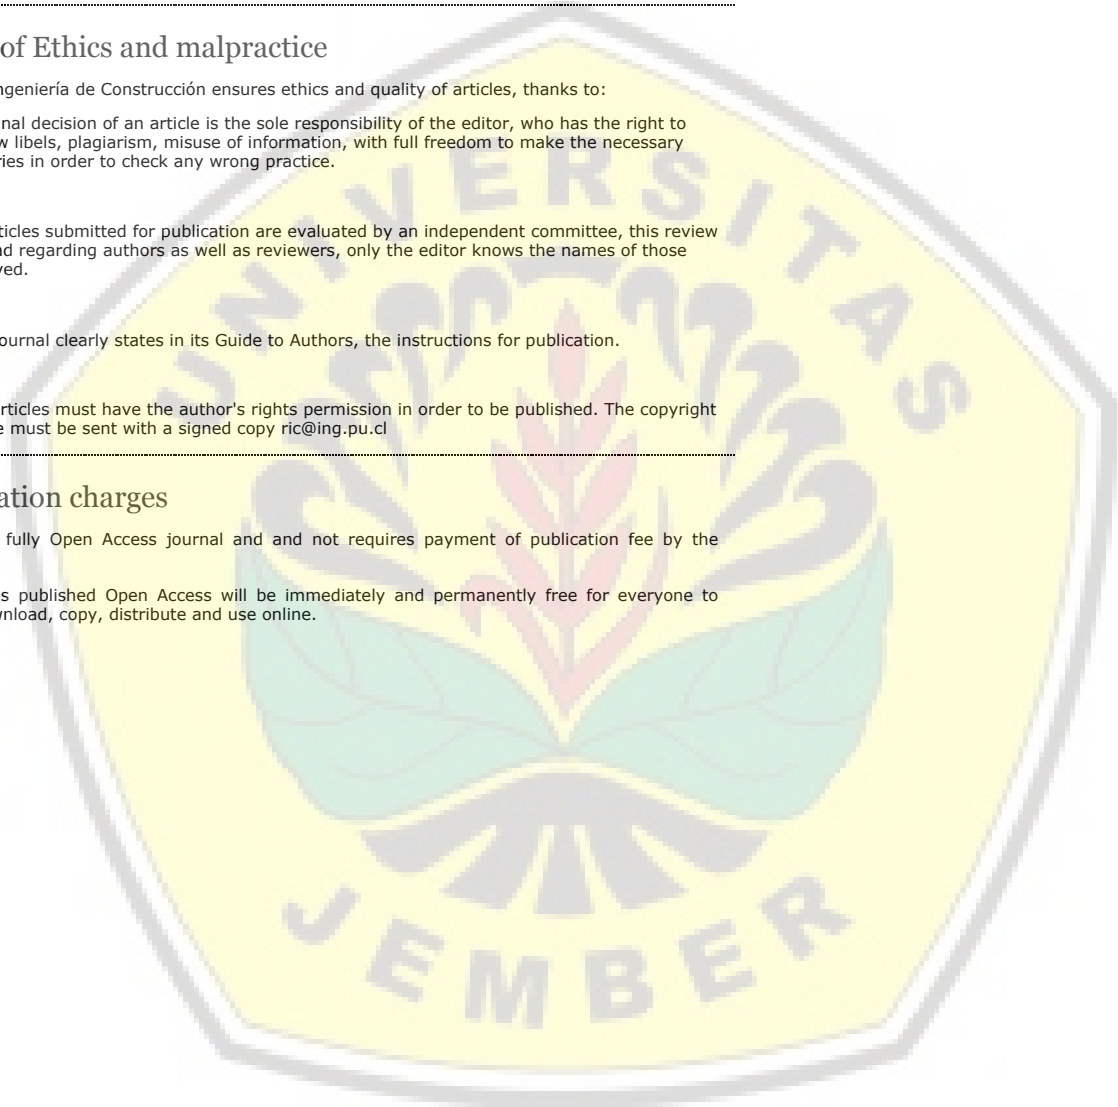

Comparison addition of rice husk ash and roof tile ash on fly ash-based geopolymer cement with portland cement

Comparación de la adición de cenizas de cascarilla de arroz y cenizas de tejas a cemento de geopolímero a base de cenizas volantes con cemento Portland

D. Nurtanto ^{1*}, I. Junaidi *, W. Wahyuningtyas *, W. Yunarni *

* Universitas Jember – Jember, INDONESIA

Fecha de Recepción: 20/04/2020

Fecha de Aceptación: 22/10/2020

PAG 287-294

Abstract

The use of Portland cement is considered a very good material for making concrete. This is because many are found in building shops and its high performance in making concrete. Research on alternative Portland cement is a worldwide priority for reducing CO emissions to the atmosphere. Alternative Portland cement is a material containing aluminosilicate which is dissolved with an alkaline solution to produce strong pozzolanic properties and replace the function of Portland cement. Natural aluminosilicates can be found in agricultural and industrial wastes. For example fly ash (FA), roof tile ash (RTA), rice husk ash (RHA), sugar cane bagasse ash (SCBA). This method estimates the development of mechanical properties of concrete with alternative portland cement with concrete with portland cement throughout the treatment process. The mechanical properties that will be seen are setting time and compressive strength. Alternative Portland cement uses the basic ingredients of fly ash aluminosilicate with an alkaline activator solution (NaOH, Na₂SiO₃) of 12 Molar. This study is based on experimental studies by replacing FA by 5% and 10% with RHA and RTA where the development of several mechanical properties will be investigated. The results show that several alternative portland cement mixes have similar mechanical properties to portland cement.

Keywords: Fly Ash; Rice Husk Ash; Roof Tile Ash; Setting Time; Compressive Strength

Resumen

El cemento Portland se considera un excelente material para la fabricación de hormigón. Por su alto rendimiento en esta elaboración se encuentra mucho en tiendas de construcción. La investigación acerca de cementos Portland alternativos tiene prioridad a nivel mundial para reducir las emisiones de CO a la atmósfera. El cemento Portland alternativo es un material que contiene aluminosilicatos disueltos en una solución alcalina para producir propiedades pozzolánicas suficientemente sólidas que reemplacen la función del cemento Portland. Los aluminosilicatos naturales se pueden encontrar en desechos agrícolas e industriales. Por ejemplo, en cenizas volantes (CV), cenizas de tejas (CT), cenizas de cascarilla de arroz (CCAr), cenizas de caña de azúcar (CCAZ). Este método compara el desarrollo de propiedades mecánicas del concreto con cemento Portland alternativo con las del concreto con cemento Portland normal, durante todo el proceso de su empleo. Las propiedades mecánicas que se revisarán son el tiempo de fraguado y la resistencia a la compresión. El cemento Portland alternativo utiliza una base de aluminosilicato de cenizas volantes con una solución alcalina activadora (NaOH, Na₂SiO₃) 12 molar. Este estudio se basa en ensayos experimentales de reemplazo de CV al 5% y 10% con CCAr y CT, en los que se investigó el desarrollo de varias propiedades mecánicas. Los resultados muestran que varias mezclas alternativas de cemento Portland tienen propiedades mecánicas similares al cemento Portland normal.

Palabras clave: Cenizas volantes; cenizas de cáscara de arroz; cenizas de azulejos; gestión del tiempo; resistencia a la compresión

1. Introduction

Cement is one of the main ingredients to make concrete, which serves as a binder with fine aggregate, coarse aggregate, and water with or without additional mixed materials. Increased use of cement can be seen with the increasing needs of concrete annually, of course, it is an adverse impact on the environment due to any cement manufacturing generated CO₂ released in the atmosphere when calcium carbonate is heated and produces lime (Amran et al., 2020)(Stafford et al., 2015).

The cement industry is a cause of one of the contributors to air pollution and other environmental pollution, one of the impacts that can be caused is the greenhouse effect that can increase global warming (Reza et al., 2013)(Hasanbeigi et al., 2012). Therefore, the use of alternative Portland cement with new cement needs to be developed. So that in the process of cement production reduces greenhouse gas emissions and energy efficiency occurs. Among these alternative materials are materials that contain many elements of silica (Si) and alumina (Al)(Torres-Carrasco and Puertas, 2017), both natural materials (clay)(Chen et al., 2016)(Yanguatin et al., 2017) or industrial waste products, such as fly ash(Yacob et al., 2019)(Gülşan et al., 2019)(Pavithra et al., 2016)(Pasupathy et al., 2017)(Muhammad et al., 2019), rice husk ash (Nuaklong et al., 2020)(Akasaki et al., 2016), sugar cane bagasse ash (Mello et al., 2020)(Fairbairn et al., 2010)(Bahurudeen et al.; 2015) (Nugroho et al.; 2017), roof tile ash (Reggiani, 2019) (Bui et al., 2017)(Rachman, 2015).

¹ Corresponding author:

Universitas Jember – Jember, INDONESIA

E-mail: dwinurtanto.teknik@unej.ac.id



The fly-ash material, rice husk ash, and dust tile press powder in the manufacture of geopolymer cement can react with the help of alkaline substances (catalysts and activators) that act as activation of polymerization processes and the release of small molecules such as H₂O to form more monomer chain bonds long. To get polymerization reactions required a reactant of the alkaline groups of Sodium Hydroxide (NaOH) and Sodium Silicate (Na₂SiO₃) which can release unnecessary ions (Torres-Carrasco and Puertas, 2017) (Zhang et al.; 2014) (Bajpai et al.; 2020). In a previous study the influence of NaOH on the setting time of the concrete that is the higher the value activators NaOH is given, then the faster its finish setting time (Risdanareni et al., 2015) (Kanaan and Soliman, 2019) (Gupta et al., 2017) (Aliabdo et al., 2016). The purpose of this research is to experimentally test the setting time performance and compressive strength of fly ash-based geopolymer concrete compared to portland cement concrete.

2. Materials and Methods

2.1 Material

Cement:

The types of cement that will be compared in this experiment are portland cement types I, II, III, IV and V. Its characteristics are following Indonesian national standards (SNI) (Badan Standardisasi Nasional-BSN, 2004). The main physical requirements of Portland cement can be seen in (Table 1).

Table 1. Major Physical Requirements of Portland Cement

Description	Types of Portland Cement				
	I	II	III	IV	V
Setting Time (alternative method) with Vicat tool					
1. Initial Time, minute, Minimum	45	45	45	45	45
2. Final Time, minute, Maximum	375	375	375	375	375
Compressive Strength :					
1. 1 Day, kg/cm ² , Minimum	-	-	120	-	-
2. 3 Day, kg/cm ² , Minimum	135	100	240	-	80
3. 7 Day, kg/cm ² , Minimum	215	175	-	70	150
4. 28 Day, kg/cm ² , Minimum	300	-	-	170	210

Aggregate:

The aggregates used are Ottawa sand with a specific gravity of 2.664 g/cm³, water absorption rate of 0.267%, modulus of fineness of 2,427 and mud content of 0.352%.

Fly Ash (FA):

Fly ash is obtained from coal combustion waste at the Paton power plant, (PLTU Paton) Probolinggo, East Java, Indonesia. Fly ash is included in class F according to the standards given by ASTM C 618 (American Society for Testing and Materials –ASTM, 2014). The chemical composition of fly ash can be seen in (Table 2).



Table 2. The Chemical Composite of Fly Ash (FA)

Chemical ingredients	Percentage (%)
SiO ₂	52,35
Al ₂ O ₃	12,11
Fe ₂ O ₃	12,35
CaO	6,79
MgO	10,63
Na ₂ O	2,15
SO ₃	2,27
H ₂ O	0,12
LOI	0,40
SiO ₂ + Al ₂ O ₃ + Fe ₂ O ₃	76,84

Rice husk ash (RHA):

Rice husks come from the Sumber Jeruk rice mill, Jember, East Java, Indonesia. To get good pozzolanic characteristics, rice husk must be burned in the range of 600°C to 850°C (Barbosa et al., 2013). In this study, rice husk was burned at ± 650°C for 24 hours. Chemical characteristics can be seen in (Table 3).

Table 3. The Chemical Composite of Rice husk ash (RHA)

Chemical ingredients	Percentage (%)
SiO ₂	79,7
Al ₂ O ₃	0,42
Fe ₂ O ₃	0,38
CaO	3,99
LOI	13,67
SiO ₂ + Al ₂ O ₃ + Fe ₂ O ₃	80,5

Roof Tile Ash:

Tile powder is obtained from a tile factory waste in the village of Kunir, Lumajang, East Java. Roof tile ash obtained from burning tile powder at a temperature of ± 900°C for 24 hours. Chemical characteristics can be seen in (Table 4).

Table 4. The Chemical Composite of Roof tile ash (RTA)

Chemical ingredients	Percentage (%)
SiO ₂	24,5
Al ₂ O ₃	17,8
Fe ₂ O ₃	4,52
CaO	7,58
LOI	15,28
SiO ₂ + Al ₂ O ₃ + Fe ₂ O ₃	46,82



2.2 Mixing method

The methodology used in this study is experimental research, which is an experiment and an error about previous research in the laboratory. The best NaOH solution is obtained for 12M. Before mixing with sodium silicate (Na_2SiO_3), NaOH solution is left for 24 hours. The ratio of the mixture between Na_2SiO_3 to NaOH is 2. (Table 5) and (Table 6) show the mixture of pasta and mortar. FA was replaced by RHA and RTA at 0%, 5% and 10%.

Table 5. The Composition for one geopolymer paste binder

Geopolymer Paste Binder Code	FA (gr)	RHA (gr)	RTA (gr)	NaOH (gr)	Na_2SiO_3 (gr)
P1	300	-	-	48.5	97
P2	285	15	-	48.5	97
P3	270	30	-	48.5	97
P4	285	-	15	48.5	97
P5	270	-	30	48.5	97

Table 6. The Composition of Mortar Geopolymer (kg/m³)

Mortar Geopolimer	Sand Ottawa	FA	RHA	RTA	NaOH	Na_2SiO_3
M1	1808,88	657,76	-	-	106,4	212,72
M2	1808,88	624,88	32,88	-	106,4	212,72
M3	1808,88	591,92	65,84	-	106,4	212,72
M4	1808,88	624,88	-	32,88	106,4	212,72
M5	1808,88	591,92	-	65,84	106,4	212,72



Figure 1. Specimens (a) pasta binder; (b) mortar binder

2.3. Casting and curing

Fresh geopolymer paste is cast in a conical cone-shaped mould, top diameter 60 mm, bottom diameter 70 mm and height 40 mm. The test specimens were kept in a humid cabinet for 30 minutes. The geopolymer mortar consists of geopolymer paste and Ottawa sand. Binder pasta, Ottawa sand and alkaline activators are mixed in a mixer until a homogeneous geopolymer mortar is obtained. Homogeneity testing of the mixture on the flow table with a flow rate requirement of 110 ± 5 mm following SNI standards (Badan Standardisasi Nasional-BSN, 2014). The geopolymer mortar was printed in a 50 mm x 50 mm x 50 mm cube and allowed to stand for 24 hours at room temperature. The mould is opened and maintained in average roomtemperature, 26^oC, until the test day.

2.4. Testing

Setting time tests are carried out on geopolymer paste according to SNI standards by enabling mechanical testing. Insert the test specimen in the Vicat device, touch the tip of the Vicat needle in the middle of the surface of the test specimen and tighten the position of the Vicat needle, place the scale reading at zero or note the starting number, and immediately remove the Vicat needle. Read the penetration of the Vicat needle into the test specimen after 30 seconds. Repeat this test every five minutes. every time a penetration attempt is made, the Vicat needle must be cleaned and in a straight condition, free from vibrations. Geopolymer mortar compressive strength test according to SNI standards (Badan Standardisasi Nasional-BSN, 2002). Before testing, the mortar is removed from the treatment area and allowed to stand for 15 minutes. Flatten the surface of the mortar so that it is flat and level with the sandpaper. Mortar compressive strength was tested at 1,3,7 and 28 days.

3. Result and discussion

3.1. Setting Time

In (Figure 2) it can be concluded that 5 proportions of geopolymer cement have a faster binding time than Portland cement, this is influenced by Sodium Hydroxide (NaOH) because the higher the activator value is given, the faster the binding time (Akasaki et al., 2016)(Pavithra et al., 2016). Pasta with 100% fly ash content (P1) has the fastest binding time. Replacing FA with RHA and RTA will slow downtime. This is influenced by the shape of the particles and their silica content (Nuaklong et al., 2020) (Pinasang et al., 2016). The spherical shape of the FA particles will increase the binding reaction, thereby reducing water usage, easily binding to each other and reducing the space between the mixed ingredients (Manjunath and Ranganath, 2019). The shape of RHA particles with holes like a sponge will require high water requirements so it is slow to react (Barbosa et al., 2013). The silica content in the RTA is smaller than the FA so the reaction is also slower (Okoye et al., 2017).

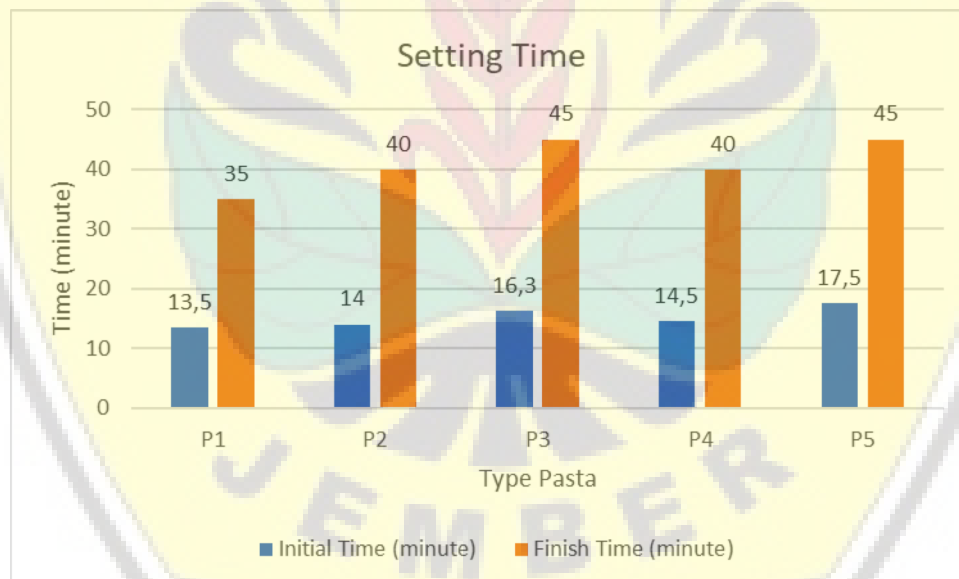


Figure 2. Setting Time

3.2. Compressive strength

In (Figure 3), for the age of 1 day the compressive strength of geopolymer cement types M1, M2, M3 and M4 according to the compressive strength for portland cement; at the age of 3 days the compressive strength of cement geopolymers, all proportions according to the compressive strength of Portland cement except portland type III cement; at 7 days the compressive strength of geopolymer cement types M1, M4 and M5, is according for portland cement; At 28 days the compressive strength of geopolymer cement, all proportions according to the Portland cement compressive strength.

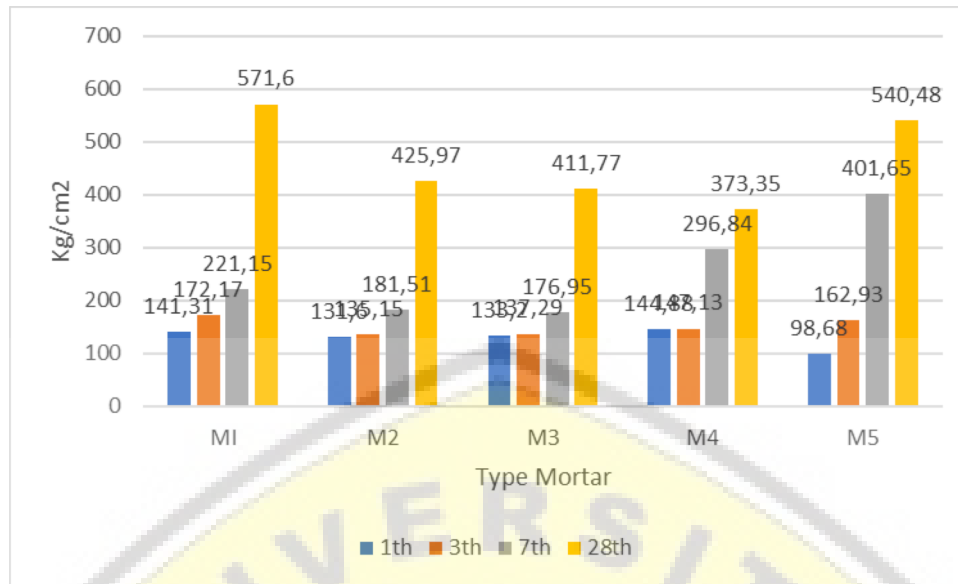


Figure 3. Compressive Strength

The determination of optimal proportion in this study was taken at the age of 28 days, which from each proportion got the best result 100% fly ash. The addition of rice husk ash and press tile powder has a strong press effect that is not too far against 100% fly ash. The addition of such ingredients sometimes gives increased and decreased compressive strength in certain ages such as at 1, 3, 7 and 28 days. At 1 day, the addition of roof tile ash (5%) gave a compressive strength higher than 100% fly ash. At 7 days old, the addition of roof tile ash of 5%, 10% powder gave a higher compressive strength than 100% fly ash. At the age of 28 days the addition of rice husk ash and roof tile ash, as well as both materials do not provide a compressive strength higher than 100% fly ash. The addition of rice husk ash to fly ash always provides a compressive strength lower than 100% fly ash. The determination of superior proportion is taken at the age of 28 days because at that age the value of compressive strength is considered stable (Badan Standardisasi Nasional-BSN, 2013). (Figure 3) shows that the superior proportion of proportion that gives high compressive strength is found 100% fly ash proportion.

4. Conclusions

In this section, in general, from the results presented in this work, we can compare the addition of rice husk ash and tile ash to geopolymer-based cement fly ash with portland cement. This research can be concluded as follows:

- From the results of making all types of geopolymer paste and mortar paste, the mixture and homogeneous flow rate meet SNI requirements for the production of geopolymer mortar.
- Geopolymer cement has a faster binding time than Portland cement. In geopolymer cement, the substitution of fly ash with rice husk ash or tile ash, the binding time is slower.
- The compressive strength test results show that geopolymer cement containing 100% fly ash can be an alternative use for Portland type I, II, IV, V; for substitution of fly ash with rice husk ash can be an alternative use for Portland type II, IV, V; for the substitution of fly ash with roof tile ash can be an alternative use for Portland types I, II, IV, and V.
- Superior geopolymer cement composition at 28 days was obtained with 100% fly ash.



5. References

- Akasaki, J.; Moraes, M.; Silva, C.; Fioriti, C.; Tashima, M. (2016).** Assessment of the maturity concept in concrete with addition of rice husk ash. *Revista Ingeniería de Construcción*, 31(3), 175–182. <https://doi.org/10.4067/S0718-50732016000300003>
- Aliabdo, A. A.; Abd Elmoaty, A. E. M.; Salem, H. A. (2016).** Effect of water addition, plasticizer and alkaline solution constitution on fly ash based geopolymer concrete performance. *Construction and Building Materials*, 121, 694–703. <https://doi.org/10.1016/j.conbuildmat.2016.06.062>
- American Society for Testing and Materials –ASTM. (2014).** C168-12a : Standard Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use. Philadelphia, United States of America.
- Amran, Y. H. M.; Alyousef, R.; Alabduljabbar, H.; El-Zeadani, M. (2020).** Clean production and properties of geopolymer concrete; A review. *Journal of Cleaner Production*, 251. <https://doi.org/10.1016/j.jclepro.2019.119679>
- Badan Standardisasi Nasional-BSN. (2004).** SNI 15-2049 : Semen portland. Jakarta, Indonesia.
- Badan Standardisasi Nasional-BSN. (2014).** SNI 6882 : Spesifikasi Mortar untuk Pekerjaan Unit Pasangan. Jakarta, Indonesia.
- Badan Standardisasi Nasional-BSN. (2002).** Sni 03-6825 : Standar Nasional Indonesia Metode pengujian kekuatan tekan mortar semen Portland untuk pekerjaan sipil. Jakarta, Indonesia.
- Badan Standardisasi Nasional-BSN. (2013).** SNI 2847: Persyaratan beton struktural untuk bangunan gedung. Jakarta, Indonesia: SNI.
- Bahurudeen, A.; Kanraj, D.; Gokul Dev, V.; Santhanam, M. (2015).** Performance evaluation of sugarcane bagasse ash blended cement in concrete. *Cement and Concrete Composites*, 59, 77–88. <https://doi.org/https://doi.org/10.1016/j.cemconcomp.2015.03.004>
- Bajpai, R.; Choudhary, K.; Srivastava, A.; Sangwan, K. S.; Singh, M. (2020).** Environmental impact assessment of fly ash and silica fume based geopolymer concrete. *Journal of Cleaner Production*, 254, 120147. <https://doi.org/10.1016/j.jclepro.2020.120147>
- Barbosa, M. B.; PEREIRA, A. M.; Akasaki, J. L.; Fioriti, C. F.; Fazzan, J. V.; TASHIMA, M. M. et al. (2013).** Impact strength and abrasión resistance of high strength concrete with rice husk ash and rubber tires. *Revista IBRACON de Estruturas e Materiais*, 6(5), 811–820. <https://doi.org/10.1590/s1983-41952013000500007>
- Bui, P. T.; Ogawa, Y.; Nakarai, K.; Kawai, K.; Sato, R. (2017).** Internal curing of Class-F fly-ash concrete using high-volume roof-tile waste aggregate. *Materials and Structures*, 50(4), 203. <https://doi.org/10.1617/s11527-017-1073-z>
- Chen, L.; Wang, Z.; Wang, Y.; Feng, J. (2016).** Preparation and Properties of Alkali Activated Metakaolin-Based Geopolymer. *Materials (Basel, Switzerland)*, 9(9), 767. <https://doi.org/10.3390/ma9090767>
- Mello, L. C.; Soares, M. A.; De Sá, M. V.; De Souza, N.; De Farias, E. C. (2020).** Effect of high temperatures on self-compacting concrete with high levels of sugarcane bagasse ash and metakaolin. *Construction and Building Materials*, 248, 118715. <https://doi.org/https://doi.org/10.1016/j.conbuildmat.2020.118715>
- Fairbairn, E. M. R.; Americano, B. B.; Cordeiro, G. C.; Paula, T. P.; Toledo Filho, R. D.; Silvano, M. M. (2010).** Cement replacement by sugar cane bagasse ash: CO2 emissions reduction and potential for carbon credits. *Journal of Environmental Management*, 91(9), 1864–1871. <https://doi.org/https://doi.org/10.1016/j.jenvman.2010.04.008>
- Gülşan, M. E.; Alzeebaree, R.; Rasheed, A. A.; Niş, A.; Kurtoglu, A. E. (2019).** Development of fly ash/slag based self-compacting geopolymer concrete using nano-silica and steel fiber. *Construction and Building Materials*, 211, 271–283. <https://doi.org/10.1016/j.conbuildmat.2019.03.228>
- Gupta, S.; Chandrakar, G.; & Ash, F. (2017).** Experimental Studies on Fly Ash Based Geopolymer Concrete without Portland Cement-An Eco Friendly Construction. *International Journal of Engineering Science and Computing*, 7(5), 11514–11520.
- Hasanbeigi, A.; Lu, H.; Williams, C.; Price, L. (2012).** International Best Practices for Pre- Processing and Co-Processing Municipal Solid Waste and Sewage Sludge in the Cement Industry. (July), 123.
- Kanaan, D. M.; Soliman, A. M. (2019).** Effect of activator composition on the performance of alkali-activated scc. *CSCE Annual Conference Growing*, 1–9.
- Manjunath, R.; Ranganath, R. V. (2019).** Performance Evaluation of Fly-ash based Self-compacting geopolymer concrete mixes. *IOP Conference Series: Materials Science and Engineering*, 561(1). <https://doi.org/10.1088/1757-899X/561/1/012006>
- Muhammad, N.; Baharom, S.; Amirah, N.; Ghazali, M.; Alias, N. A. (2019).** Effect of Heat Curing Temperatures on Fly Ash-Based Geopolymer Concrete. *International Journal of Engineering & Technology*, 8(January), 15–19.
- Nuaklong, P.; Jongvitsakul, P.; Pothisiri, T.; Sata, V.; Chindaprasit, P. (2020).** Influence of rice husk ash on mechanical properties and fire resistance of recycled aggregate high-calcium fly ash geopolymer concrete. *Journal of Cleaner Production*, 252. <https://doi.org/10.1016/j.jclepro.2019.119797>
- Nugroho, A.; Rahman Saleh, A.; Rawamangun Muka, J.; Timur Surel, J. (2017).** Utilization of Baggase Ash on Lightweight Foamed Concrete. *Jurnal Permukiman*, 12(1), 20–24.
- Okoye, F. N.; Prakash, S.; Singh, N. B. (2017).** Durability of fly ash based geopolymer concrete in the presence of silica fume. *Journal of Cleaner Production*, 149, 1062–1067. <https://doi.org/10.1016/j.jclepro.2017.02.176>
- Pasupathy, K.; Berndt, M.; Sanjayan, J.; Rajeev, P.; Cheema, D. S. (2017).** Durability of lowcalcium fly ash based geopolymer concrete culvert in a saline environment. *Cement and Concrete Research*, 100(January), 297–310. <https://doi.org/10.1016/j.cemconres.2017.07.010>
- Pavithra, P.; Srinivasula Reddy, M.; Dinakar, P.; Hanumantha Rao, B.; Satpathy, B. K.; Mohanty, A. N. (2016).** A mix design procedure for geopolymer concrete with fly ash. *Journal of Cleaner Production*, 133, 117–125. <https://doi.org/10.1016/j.jclepro.2016.05.041>
- Pinasang, D. B.; Sompie, O. B.; Jansen, F. (2016).** Analisis campuran kapur-fly ash dan kapur-abu sekam padi terhadap lempung ekspansif. *Media Engineering*, 6(2), 157–178.
- Rachman, F. (2015).** Penggunaan Abu Sekam Padi Dan Abu Batu Pada Pembuatan Genteng Beton (Jember University). Retrieved from <http://repository.unej.ac.id/handle/123456789/72801>
- Reggiani, A. (2019, January 2).** Geopolymer roof tile. *Proceedings of the 42nd International Conference on Advanced Ceramics and Composites*, pp. 225–232. <https://doi.org/doi:10.1002/9781119543381.ch20>
- Reza, B.; Soltani, A.; Ruparathna, R.; Sadiq, R.; Hewage, K. (2013).** Environmental and economic aspects of production and utilization of RDF as alternative fuel in cement plants: A case study of Metro Vancouver Waste Management. *Resources, Conservation and Recycling*, 81, 105–114. <https://doi.org/10.1016/j.resconrec.2013.10.009>



- Risdanareni, P.; Ekaputri, J. J.; Triwulan. (2015).** The Influence of Alkali Activator Concentration to Mechanical Properties of Geopolymer Concrete with Trass as a Filler. *Geopolymer and Green Technology Materials*, 803, 125–134. <https://doi.org/10.4028/www.scientific.net/MSF.803.125>
- Stafford, F. N.; Viquez, M. D.; Labrincha, J.; Hotza, D. (2015).** Advances and Challenges for the Co-processing in Latin American Cement Industry. *Procedia Materials Science*, 9, 571–577. <https://doi.org/10.1016/j.mspro.2015.05.032>
- Torres-Carrasco, M.; Puertas, F. (2017).** Alkaline activation of different aluminosilicates as an alternative to Portland cement: Alkali activated cements or geopolymers. *Revista Ingeniería de Construcción*, 32(2), 5–12. <https://doi.org/10.4067/S0718-50732017000200001>
- Yacob, N. S.; ElGawady, M. A.; Sneed, L. H.; Said, A. (2019).** Shear strength of fly ash-based geopolymer reinforced concrete beams. *Engineering Structures*, 196 (August 2018), 109298. <https://doi.org/10.1016/j.engstruct.2019.109298>
- Yanguatin, H.; Tobón, J.; Ramírez, J. (2017).** Pozzolanic reactivity of kaolin clays, a review | Reactividad puzolánica de arcillas caolínicas, una revisión. *Revista Ingeniería de Construcción*, 32 (2), 13–24.
- Zhang, Z.; Provis, J. L.; Reid, A.; Wang, H. (2014).** Geopolymer foam concrete: An emerging material for sustainable construction. *Construction and Building Materials*, 56, 113–127. <https://doi.org/10.1016/j.conbuildmat.2014.01.081>

