



# Jurnal ILMU DASAR

FMIPA Universitas Jember

Terakreditasi SINTA Kemendikbud No. 21/E/KPT/2018

eISSN 2442-5613 pISSN 1411-5735

[ANNOUNCEMENTS](#)[CURRENT](#)[ARCHIVES](#)[ABOUT](#) ▾


## CURRENT ISSUE

**Vol 20 No 1 (2019)**



Jurnal ILMU DASAR (JID) is a national peer-reviewed and open access journal that publishes research papers encompasses all aspects of natural sciences including Mathematics, Physics, Chemistry and Biology JID publishes 2 issues in 1 volume per year. First published, volume 1 issue 1, in

January 2000 and available in electronically since 2012. Jurnal ILMU DASAR is accredited by the Ministry of Research, Technology and Higher Education of the Republic of Indonesia (RISTEKDIKTI), No. 21/E/KPT/2018 (July. 9, 2018). All accepted manuscripts will be published worldwide JID has been indexed in:

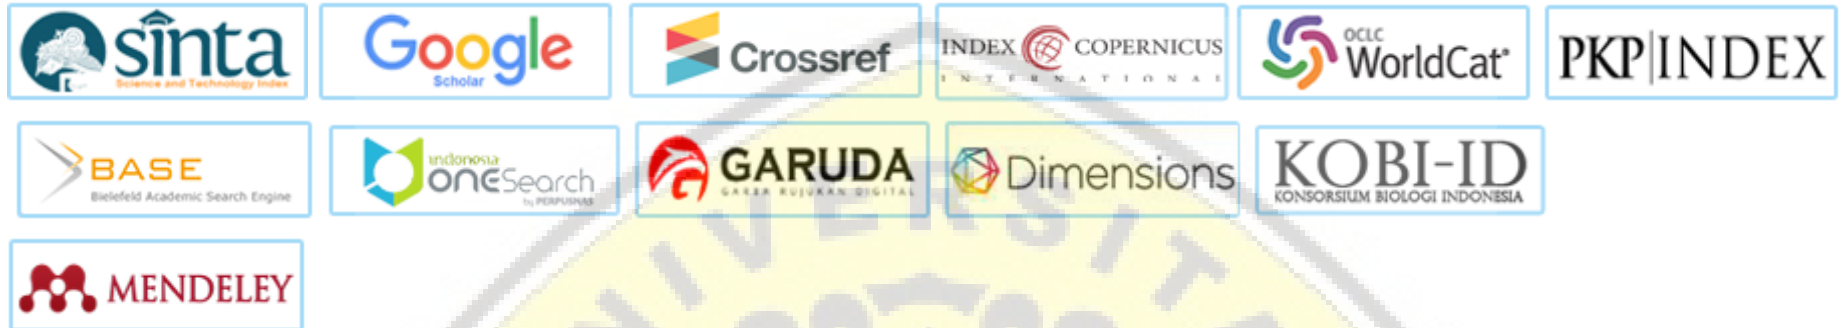

Jurnal ILMU DASAR has been collaborated in Konsorsium Biologi Indonesia since 2017.

#### Authors Index:

Ahmad Kamsyakawuni, 53; Alan Prahutama, 47; Alfian Futuhul Hadi, 19; Andi Hairil Alimuiddin, 39; Anis Shofiyani, 39; Annisa Rahmita S., 33; Bambang Piluharto, 25; Darso Sugiono, 1; Dian Anggraeni, 53; Dwi Ispriyanti, 47; Eka Rahmawati Syaidah, 7; Endarko, 61; Fara Chitra, 39; Intan Syahbanu, 25; Lidia Maziyyatun Nikmah, 13; Lutfi Afifah, 1; Lutvia Citra Ramadhani, 53; Mahriani, 13; Mohamad Fatekurohman, 19; Nova Hariani, 7; Rudiyanasyah, 39; Sadjidon, 33; Siti Rabi'atul Adawiyah, 61; Sudarko, 25; Sunarsini, 33; Suparti, 47; Sus Trimurti, 7; Susantin Fajariyah, 13; Syahrul Khairi, 25; Tiani Wahyu Utami, 47; Toto Hermanto, 25; Veniola Forestryani, 19; Winda Rahmalia, 39.

PUBLISHED: 2019-01-23

## GENERAL

### Fluctuation of Insect Population on Rice Field in Pangkalan Sub-district Karawang Regency: Indicator for Environmental Health

Lutfi Afifah, Darso Sugiono

1-6

 PDF

**Laboratory Study of Oviposition Preference of *Aedes aegypti* (Linnaeus, 1762) in Waste Settlement**

Nova Hariani, Eka Rahmawati Syaidah, Sus Trimurti

7-12

 PDF**The Effect of Ethanol Extract Turmeric Rhizome (*Curcuma Longa*) to Histological Structure of Rat Rectum Induced Dextran Sodium Sulphate (DSS)**

Lidia Maziyyatun Nikmah, Susantin Fajariyah, M. Mahriani

13-18

 PDF**Survival Analysis of Sea Turtles Eggs Hatching Success using Cox non Proportional Hazard Regression**

Veniola Forestryani, Mohamad Fatekurohman, Alfian Futuhul Hadi

19-24

 PDF**Preparation and Characterization of Polysulfone/Celullose Acetate (PSF/CA) Blend Membrane**

Intan Syahbanu, Bambang Piluharto, Syahrul Khairi, S. Sudarko, Toto Hermanto

25-32

 PDF**Weakly Contractive Mapping and Weakly Kannan Mapping in Partial Metric Space**

S. Sunarsini, S. Sadjidon, Annisa Rahmita

33-38

 PDF

---

**Synthesis of Nanosilica from Padas Stone to Reduce The Total Organic Carbon of Palm Oil Waste**

Anis Shofiyani, Fara Chitra, Winda Rahmalia, R. Rudiyanayah, Andi Hairil Alimuddin

39-46

 PDF

---

**Modelling Inflation Sectors in Indonesia Using Vector Autoregressive (VAR)**

Alan Prahutama; S. Suparti; Dwi Ispriyanti, Tiani Wahyu Utami

47-52

 PDF

---

**Saxena-Easo Fuzzy Time Series on Indonesia's Inflation Rate Forecasting**

Lutvia Citra Ramadhani, Dian Anggraeni, Ahmad Kamsyakawuni

53-60

 PDF

---

**Experimental Study of TiO<sub>2</sub> Nanoparticles Fabrication by Sol-gel and Co-precipitation Methods for TiO<sub>2</sub>/SnO<sub>2</sub> Composite Thin Film as Photoanode**


E. Endarko, Siti Rabi'atul Adawiyah

61-66

 PDF

---

**VIEW ALL ISSUES** >

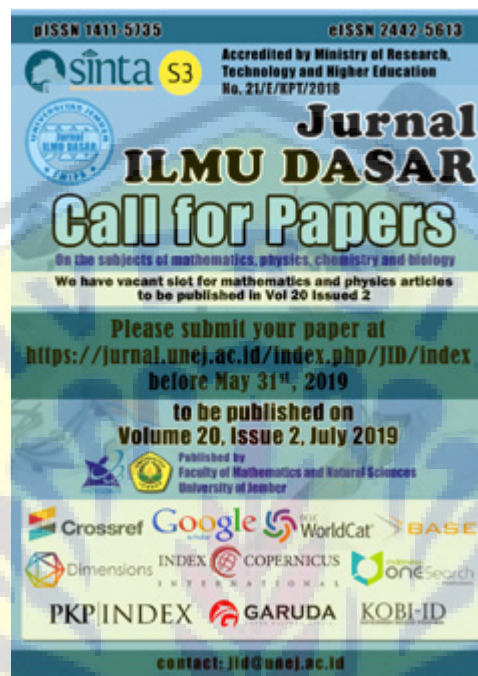

---

**Additional Menus**

---

**Journal Contact**

---

**Editor**

---

**Focus and Scope**

---

**Journal SOP**

---

**Guidelines for Reviewer**

---

**Reviewer Process**

**Online Submission**

**Make Submission**

**Publication Ethics**

**Open Access Policy**

**Journal History**

**Screening for Plagiarism**

**Indexing Service**


**Visitor Statistics**

**Supplementary Files**

**Statement of Originality**

**Reviewer Form**

**ISSN Barcode**



Online:

ISSN 2442-5613



9 772442 561005

Print:

ISSN 1411-5735



9 771411 573001



**we are**



# Crossret



# Member

---

Journal Template

---





## Tools



## INFORMATION

For Readers

For Authors

For Librarians

## Journal Visitor



00045314



**Jurnal ILMU DASAR Published by Fakultas MIPA Universitas Jember**  
is licensed under a [Creative Commons Attribution-ShareAlike 4.0 International License](https://creativecommons.org/licenses/by-sa/4.0/).





# Jurnal ILMU DASAR

FMIPA Universitas Jember

Terakreditasi SINTA Kemenristekdikti No. 21/E/KPT/2018

eISSN 2442-5613 pISSN 1411-5735

[ANNOUNCEMENTS](#)[CURRENT](#)[ARCHIVES](#)[ABOUT ▾](#)

[HOME](#) / [Editorial Team](#)

## Editor

1. Purwatiningsih, The University of Jember, Indonesia / **Chief Editor**  
SCOPUS ID. [55341566700](#) - [Google Scholar Profile](#) - Sinta ID. [5982555](#)
2. Dwi Indarti, The University of Jember, Indonesia  
[Google Scholar Profile](#)
3. Eva Tyas Utami, The University of Jember, Indonesia  
[Google Scholar Profile](#)
4. Supriyadi, The University of Jember, Indonesia  
[Google Scholar Profile](#) - Sinta ID. [5998109](#)
5. Dian Anggraeni, The University of Jember, Indonesia  
[Google Scholar Profile](#) - Sinta ID. [6014770](#)
6. Kahar Muzakhar, The University of Jember, Indonesia  
SCOPUS ID. [56737119300](#) - [Google Scholar Profile](#) - Sinta ID. [5989819](#)
7. Muhammad Fatekuraahman, The University of Jember, Indonesia

[Google Scholar Profile](#) - Sinta ID. [6037857](#)

8. Bambang Piluharto, The University of Jember, Indonesia

SCOPUS ID. [37056268800](#) - [Google Scholar Profile](#) - Sinta ID. [5993961](#)

9. Artoto Arkundato, The University of Jember, Indonesia

SCOPUS ID. [22933701900](#) - [Google Scholar Profile](#) - Sinta ID. [5994932](#)

10. Siswoyo - The University of Jember, Indonesia

SCOPUS ID. [57193830395](#) - [Google Scholar Profile](#) - Sinta ID. [257755](#)

11. Yoyok Yulianto, The University of Jember, Indonesia / Web Maintenance

### Reviewer

1. Chang-Su Park, Catholic University of Daegu, Department of Food Science and Technology, Gyeongsan, South Korea

SCOPUS ID. [34973170600](#)

2. Srinivasan Ramasamy, World Vegetable Centre, Shanhua Tainan, Taiwan

SCOPUS ID. [39561441000](#) - [Google Scholar Profile](#)

3. Intan Ahmad, Bandung Institute of Technology, Indonesia

SCOPUS ID. [57199666916](#) - [Google Scholar Profile](#) - Sinta ID. [18586](#)

4. Irminda Kris Murwani, ITS Surabaya, Indonesia

SCOPUS ID. - [6603061145](#) - [Google Scholar Profile](#) - Sinta ID. [5975665](#)

5. Widodo- Brawijaya University, Indonesia

SCOPUS ID. - [57190247745](#) - [Google Scholar Profile](#) - Sinta ID. [5982480](#)

6. Bambang Irawan, Airlangga University, Indonesia

SCOPUS ID. [6508239454](#) - [Google Scholar Profile](#) - Sinta ID. [5984560](#)

7. Ni Nyoman Tri Puspaningsih, Airlangga University, Indonesia

SCOPUS ID. [23006120200](#) - [Google Scholar Profile](#) - Sinta ID. [5987035](#)

8. I Gede Putu Wirawan, Udayana University, Indonesia

SCOPUS ID. [7801466336](#) - [Google Scholar Profile](#) - Sinta ID. [5987692](#)

9. Sutrisno, University of Jambi, Indonesia

SCOPUS ID. [7801466336](#) - [Google Scholar Profile](#) - Sinta ID. [6032103](#)

10. Asni Johari, University of Jambi, Indonesia

SCOPUS ID. [56603909900](#) - [Google Scholar Profile](#)

11. Didik Sulistyanto, The University of Jember, Indonesia

SCOPUS ID: [6506964916](#) - [Google Scholar Profile](#) - Sinta ID. [6013751](#)

12. Bambang Sugiharto, The University of Jember, Indonesia

SCOPUS ID: [6602309159](#) - [Google Scholar Profile](#) - Sinta ID. [6083420](#)

13. Agus Subekti, The University of Jember, Indonesia

SCOPUS ID: [6602710755](#) - [Google Scholar Profile](#) - Sinta ID. [55068](#)

14. Kusno, The University of Jember, Indonesia

[Google Scholar Profile](#)

15. Slamir, The University of Jember, Indonesia

SCOPUS ID: [7409555666](#) - [Google Scholar Profile](#) - Sinta ID. [55671](#)

16. Dafik, The University of Jember, Indonesia

SCOPUS ID: [24281263600](#) - [Google Scholar Profile](#) - Sinta ID. [5982062](#)

17. Suratno, The University of Jember, Indonesia

[Google Scholar Profile](#) - Sinta ID. [5986355](#)

18. Ramadhani Eka Putra, Bandung Institute of Technology (ITB), Indonesia

SCOPUS ID: [26326479700](#) - [Google Scholar Profile](#) - Sinta ID. [5998784](#)

19. Purkan, Airlangga University, Indonesia

[Google Scholar Profile](#) - Sinta ID. [5983068](#)

20. Titik Taufikurohmah, UNESA, Indonesia

[Google Scholar Profile](#) - Sinta ID. [259056](#)

21. Rahmat Gunawan, Mulawarman University, Indonesia

[Google Scholar Profile](#) - Sinta ID. [5975285](#)

22. Sujito, The University of Jember, Indonesia

[Google Scholar Profile](#) - Sinta ID. [6009313](#)


23. Achmad Sjaifullah, The University of Jember, Indonesia

[Google Scholar Profile](#) - Sinta ID. [55272](#)

24. Kahar Muzakhar, The University of Jember, Indonesia

SCOPUS ID. [56737119300](#) - [Google Scholar Profile](#) - Sinta ID. [5989819](#)

25. Muhammad Fatekurahman, The University of Jember, Indonesia  
[Google Scholar Profile](#) - Sinta ID. [6037857](#)
26. Kristiana Wijaya, The University of Jember, Indonesia  
SCOPUS ID. [36807253400](#) - [Google Scholar Profile](#)
27. Bambang Piluharto, The University of Jember, Indonesia  
SCOPUS ID. [37056268800](#) - [Google Scholar Profile](#) - Sinta ID. [5993961](#)
28. Artoto Arkundato, The University of Jember, Indonesia  
SCOPUS ID. [22933701900](#) - [Google Scholar Profile](#) - Sinta ID. [5994932](#)
29. Siswoyo - The University of Jember, Indonesia  
SCOPUS ID. [57193830395](#) - [Google Scholar Profile](#) - Sinta ID. [257755](#)
30. Purwatiningsih, The University of Jember, Indonesia  
SCOPUS ID. [55341566700](#) - [Google Scholar Profile](#) - Sinta ID. [5982555](#)

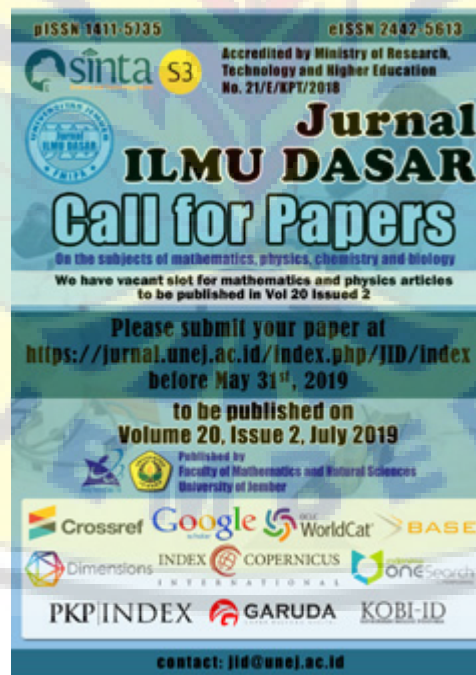

## Additional Menus

---

**Journal Contact**

**Editor**

**Focus and Scope**

**Journal SOP**

**Guidelines for Reviewer**

**Reviewer Process**

**Online Submission**

**Make Submission**

**Publication Ethics**

**Open Access Policy**

**Journal History**

**Screening for Plagiarism**

**Indexing Service**

**Visitor Statistics**

---

## Supplementary Files

### Reviewer Form

#### ISSN Barcode

Online:

ISSN 2442-5613



9 772442 561005

Print:

ISSN 1411-5735



9 771411 573001





**we are  
Crossref**

**Member**

---

Journal Template

---



---

Tools

---



---

**INFORMATION**

---

For Readers

For Authors

For Librarians

---


Journal Visitor

---



00045314

[View JID Stats](#)



**Jurnal ILMU DASAR** Published by **Fakultas MIPA Universitas Jember**  
is licensed under a [Creative Commons Attribution-ShareAlike 4.0 International License](#).



## Preparasi dan Karakterisasi Blend Membran Polisulfon/Selulosa Asetat (PSF/CA)

### *Preparation and Characterization of Polysulfone/Celulose Acetate (PSF/CA) Blend Membrane*

Intan Syahbanu<sup>1\*)</sup>, Bambang Piluharto<sup>2</sup>, Syahrul Khairi<sup>3</sup>, Sudarko<sup>2</sup>, Toto Hermanto<sup>1</sup>

<sup>1</sup>Department of Chemistry, Faculty of Mathematics and Natural Science,  
University of Tanjungpura

<sup>2</sup>Department of Chemistry, Faculty of Mathematics and Natural Science, University of Jember

<sup>3</sup>Department of Chemical Engineering, Faculty of Technique, University of Tanjungpura

\*E-mail: intan.syahbanu@chemistry.untan.ac.id

### ABSTRACT

Blend polysulfone (PSF)/cellulose acetate (CA) membranes have prepared by phase inversion method. In here, CA was prepared from bacterial cellulose by acetylation reaction. Various temperature of coagulation bath were used as variable to investigated water uptake, water flux, porosity and thermal properties of membranes. As comparison, the CA commercial (CCA) was also investigated with the same parameters. As the result, the functional group analysis by FTIR show that CA has successfully prepared from bacterial cellulose. The parameters include water uptake, water flux and porosity have the similar trend. The parameters increase with increasing of temperature of coagulation bath. The other hand, CCA membrane have similar trend to CA membranes for parameter of water water uptake, water flux and porosity. However, CCA membrane is higher than CA membranes for all parameters. Thermal analysis by Differential Scanning (DSC) showed that all blend membranes with different temperature of coagulation bath have single transition glass temperature (T<sub>g</sub>) that indicated that molecular homogeneity.

**Keywords:** blend membrane, phase inversion, coagulation bath, water flux, porosity.

### INTRODUCTION

One of important ultrafiltration (UF) membrane materials, Cellulose Acetate (CA) offers unique advantages of good hydrophilicity, antifouling property, abundance source, and biological degradation (Pang *et al.*, 2015). Despite these advantages, CA has weaknesses in thermal and chemical stability (Saljoughi *et al.*, 2010) and low mechanical properties (Ahmad *et al.*, 2015). Many studies have been undertaken to improve CA characters. For example, introduce polyethyleneglycol (PEG) to CA solution increasing pure water flux in filtration, and improve thermal/mechanical stability of membranes due to increasing T<sub>g</sub> by restriction of CA rotation (Shivakumar *et al.*, 2006; Saljoughi *et al.*, 2010). Another research were comparing PEG with aliphatic hyperbranch polyester to CA, resulting higher thermal and mechanical properties, instead, lower water flux (Mahdavi *et al.*, 2015).

In most studies in polymer chemistry, UF membranes were performed by synthetic CA, which is less biodegradable and environmentally friendly (Shivakumar *et al.*, 2006; Saljoughi *et al.*, 2010; Peng *et al.*,

2010; Mansourizadeh and Asad, 2014; Mahdavi *et al.*, 2015; Ahmad *et al.*, 2015). The development of renewable resource CA has been carried out, but it remains limited to several renewable resources, such as refined fibers, deinked newspapers, bacterial cellulose, and cellulosic waste (Fei *et al.*, 2015; Nedjma *et al.*, 2012; Radiman and Yuliani, 2008).

In this study, bacterial cellulose (BC) was naturally produced through the fermentation of coconut water using *Acetobacter xylinum*. BC was more easily acetylated due to high purity and no delignification process (Radiman and Yuliani, 2008). This study suggests that renewable resourcederived CA gives such benefits as environmental friendliness, sustainability, and relatively low cost.

Polysulfone (PSF) is a commercially available material possessing high toughness, thermal and mechanical stability, and is used universally for the fabrication of high-performance ultrafiltration (Liu, 2017), however, it is so highly hydrophobic that it is vulnerable to fouling. The improvement of PSF characters has been done in several way such as impregnating PSF with nanoparticles such as silver, TiO<sub>2</sub>, ZrO<sub>2</sub>, SiO<sub>2</sub>, (Zodrow *et al.*,

2009 ; Richards *et al*, 2012) or blending it with hydrophilic polymers such as nanocellulose (Zhong *et al*, 2015) and cellulose acetate (Shivakumar *et al*, 2006).

Blend membrane has been a simple processing method for blending two or more polymers in order to obtain desired characters of membranes. Blend membranes can be prepared through the phase inversion technique (Shivakumar *et al*, 2006; Saljoughi *et al*, 2010; Peng *et al*, 2010; Mansourizadeh and Asad, 2014). Membrane solution was cast into glass plate and immersed in a coagulation bath, and then solidification began. This wet phase inversion process was influenced to membrane character by condition of post-treatment after solidification (Mansourizadeh and Asad, 2014), evaporation times (Holda *et al*, 2013), and coagulation bath temperature (Saljoughi *et al*, 2010; Peng *et al*, 2010).

In the present study, blend membranes of PSF/CA were prepared through the thermal/wet phase inversion technique. Acetylated bacterial cellulose from coconut water was taken as a source of CA. PEG-400 was added to the system for the formation of pore (Shivakumar *et al*, 2006; Saljoughi *et al*, 2010). The effect of coagulation bath temperature on water uptake (%), water flux, pore character and thermal properties of membranes were also investigated.

## METHODS

### Materials

Sucrose (food grade sugar) and coconut water in this research were obtained from a traditional market. *Acetobacter xylinum* was obtained from Biology Laboratory of State University of Semarang, Indonesia. N-Methyl-2-Pyrrolidone (NMP), Polyethyleneglycol (PEG-400), Sulfuric Acid, Acetic Anhydride, and Glacial Acetic Acid were obtained from Merck. Commercial cellulose acetate and Polysulfone (PSF) (BM ~ 35.000) were obtained from Sigma Aldrich.

Synthesis of Bacterial Cellulose and Cellulose Acetate were taken place at Chemistry Laboratory of Tanjungpura University. Blend membranes PSF/CA and PSF/CCA were prepared and characterized at Chemistry Laboratory and CDAST Laboratory of University of Jember.

### Preparation of Bacterial Cellulose

Bacterial cellulose was prepared through the fermentation of coconut water by *Acetobacter xylinum* following Radiman and Yuliani (2008). Gels were pressed to reduce water and dried at 80 °C before an acetylation process began.

### Acetylation

The modification of bacterial cellulose was made through the acetylation process using acetic anhydride as a precursor. Sulfuric acid was added in a small portion as a catalyst (Nedjma *et al*, 2012; Fei *et al*, 2015). 5 grams of the bacterial cellulose was cut into small pieces and placed on three neck flasks. The glacial acetic acid with an amount of 100 mL was added to the system then stirred at 45 °C for 2 hours. 16 mL of glacial acetic acid again and 0.2 mL of sulfuric acid were added to the system, stirred for an hour. The system had cooled into 18 °C. Acetic anhydride (27 mL) and sulfuric acid (0.3 mL) were added to the system and stirred at 60 °C for 6 hours. The mixture was filtered to separate undissolved part, and water was added to the brown solution to cease reaction. The final product was filtered and washed until neutral pH was obtained and then dried at 50 °C. The degree of substitution was determined by acid base titration (Nedjma *et al*, 2012). The acetylated bacterial cellulose was ready to use for the blend membranes.

### Functional Group Analysis by Fourier Transform Infra Red (FTIR)

The functional groups of bacterial cellulose, commercial cellulose acetate (Sigma Aldrich) and cellulose acetate from bacterial cellulose were measured using FT-IR Bruker Alpha with RT-DLaTGS ZnSe detector. The spectra were recorded in 400 – 4000 cm<sup>-1</sup>.

### Preparation of Blend Membranes

Blend membranes were prepared by the thermal/wet phase inversion technique at different coagulation bath temperature (CBT). PEG-400 and NMP were introduced as pore forming agent and solvent, respectively. Acetylated bacterial cellulose (CA) were used with a composition of blend membranes PSF/PEG/CA/NMP (%wt) were 17/5/5/73. The solution of the blend membranes was cast into glass plate and coagulated at 27 °C, 40 °C, and 60 °C. Then, the membranes were transferred into different fresh water to remove excess solvent. Commercial cellulose acetate was taken as a comparison of the blend membranes. Different coagulation bath temperatures were used as a variable to study water uptake, water flux, and thermal properties of PSF/CA blend membranes.

### Determination of water uptake

Dried membranes were cut into small pieces, weighed, and defined as dry weight (W<sub>D</sub>). Then, they were immersed into fresh water for 24 hours, weighed, and defined as wet weight (W<sub>w</sub>). The percentage of water uptake was determined by (1).

$$w \quad (\%) = \frac{W_w - W_D}{W_D} \quad (1)$$

### Water Flux

Water flux was examined using the dead-end ultrafiltration cell with pressure at 150 kPa. The blend membranes were placed at the bottom of the

reactor with diameter 5,5 cm. Water flux was determined by pure water flux (J) (2), where V was defined as the volume of pure water passed through membranes (L); A was defined as membranes areas (m<sup>2</sup>); and t (h) was defined as sampling time for water passed through the membranes.

$$J = \frac{V}{A \cdot \Delta t} \quad (2)$$

**Membrane porosity and mean pore size**

Porosity (ε) of membrane was determined by gravimetric method, using equation (3) (Golpour *et al.*,2017) .

$$\epsilon(\%) = \frac{\omega_1 - \omega_2}{A \cdot l \cdot \rho_w} \quad (3)$$

where, ω<sub>1</sub> and ω<sub>2</sub> were wet and dry membrane, respectively. Surface area (m<sup>2</sup>) of membrane was A, and thickness (m) of membrane was l. Density of water (ρ<sub>w</sub>) was 998 kg/m<sup>3</sup>.

Mean pore radius (r<sub>m</sub>) of membrane was determined using Guerout-Elford-Ferry equation (eq.4) (Golpour *et al.*,2017).

$$r_m = \sqrt{\frac{(2.9 - 1.7 \epsilon) \eta Q}{A \cdot \epsilon \cdot \Delta P}} \quad (4)$$

where, ε, A and l obtained from porosity data, η is viscosity of water (8,9x10<sup>-4</sup> Pa s), Q is the volume permeated through membrane and P is operating pressure (1,5 bar).

**Thermal Analysis**

The thermal behaviour of samples was carried out using Differential Scanning Calorimetry (DSC 8230, Rigaku) from 30 °C tp 350 °C with heating rate 5 °C/min.

**RESULT AND DISCUSSION**

The synthesis of bacterial cellulose used coconut water as medium for *Acetobacter xylinum*. The bacterial cellulose acetate was synthesized by the modification of bacterial cellulose through the acetylation process. The blend membranes of PSF/CA were produced by the phase inversion technique at different coagulation bath temperatures.

**FTIR analysis of Bacterial Cellulose**

The bacterial cellulose (BC) was obtained during anincubation time of 6 days period resulting cellulose pellicle with a thickness of 3-4 mm (Figure1A). To illustrate the structure of BC, spectra FTIR is shown in Figure 1B. According to spectra in Figure1B, there were characteristic peaks of cellulose structure.

Peaks at 3352.97; 2922.06; 1425.80; 1159.47 and 1030.30 cm<sup>-1</sup> correspond to hydroxyl groups, C-H stretching, CH<sub>2</sub> bending, C-O-C stretching and C-O stretching in cellulose respectively. This spectra result is similar to Halib *et al.* study (2012) (Table 1), confirming that bacterial cellulose was succesfully synthesized.

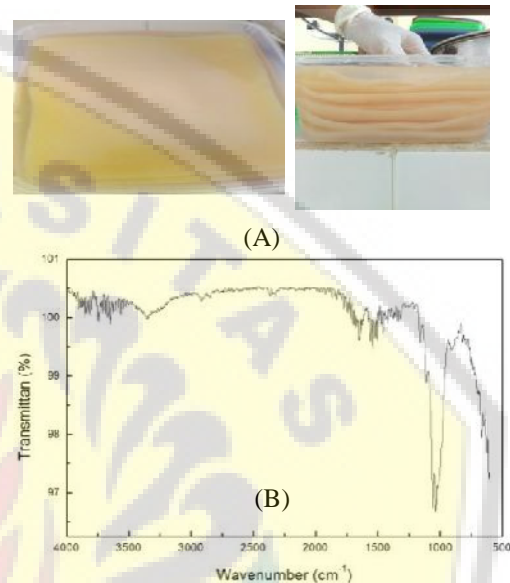


Figure 1. (A) Wet Bacterial Cellulose and (B) FTIR Spectra of Bacterial Cellulose

**FTIR analysis of cellulose acetate**

The bacterial cellulose (BC) had good purity thus, no further purification was needed before acetylation process. Physically, after the acetylation process, white powder was obtained. However, it turned to slightly brown after drying process. Figure2 shows cellulose acetate after the acetylation and drying process.

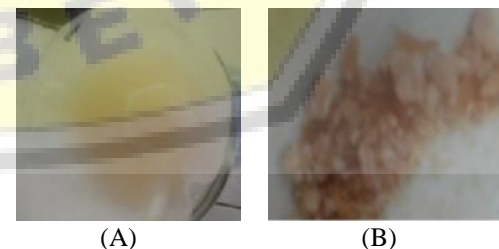


Figure 2. Cellulose acetate, (A) after acetylation and (B) after drying.



Table 1. Infrared band assignment of cellulose materials

Wavenumber (cm <sup>-1</sup> )				
Bacterial Cellulose (BC) (cm <sup>-1</sup> )	Bacterial Cellulose* (cm <sup>-1</sup> )	Cellulose Acetate (CA) (cm <sup>-1</sup> )	Commercial Cellulose Acetate (CCA) (cm <sup>-1</sup> )	Assignment
3352.97	3440	-	-	O-H Stretching
2922.06	2926	-	-	C-H Stretching
-	-	1745.34	1745.40	C=O Stretching
1547.58	-	1540.88	1540.30	Benzene ring vibrations
1425.80	1440	-	-	CH <sub>2</sub> Bending
-	1300	1369,57	1370,35	-C-CH <sub>3</sub>
-	-	1231,10	1231,28	C-O acetyl
1159.47	1163	-	-	C-O-C Stretching
1030.30	1040	1044,31	1042,69	C-O Stretching in cellulose

Nedjma *et al* , 2012; Halib *et al* ., 2012; Radiman and Yuliani, 2008

To confirm cellulose acetate structure obtained, FTIR was used for functional groups analysis. FTIR spectra results are presented in Figure 3. Both CA and CCA at 1745.34, 1369.57, and 1231.10 confirmed for the carboxylic groups (C=O) ;(-C-CH<sub>3</sub>) and CO acetyl, respectively (Radiman and Yuliani, 2008). Table 1 shows infrared band of materials. Degree of substitution of CA and CCA was found at 3,5 determined by acid base titration, indicating the product was cellulose triacetate.

cellulose acetate (CA). Peak at 3352.97 (Figure 1B) was hydroxyl groups of cellulose, which disappeared in CA and CCA (Figure 3A and 3B). The characteristics of cellulose acetate were confirmed by peak of carboxylic ester and acetyl group (Nedjma *et al*, 2012).

**Water Uptake, Water Flux and Porosity analysis of PSF/CA blend membranes**

Water uptake was used to analyze affinity to water of the blend membranes. As a hydrophobic polymer, polysulfone had very low affinity to water. Blending PSF with hydrophilic polymers like CA tends to lower hydrophobicity of PSF. Figure 4 shows water uptake (%) of the membranes.

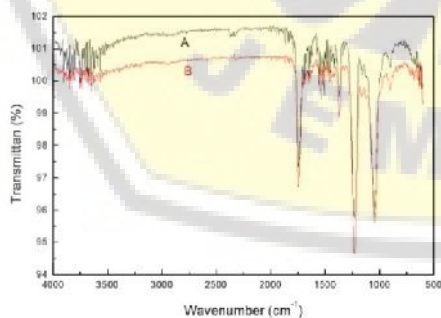


Figure 3. FTIR spectra of (A) the commercial cellulose acetate (CCA); (B) cellulose acetate from bacterial cellulose (CA)

As seen in Figure 3, there were characteristic peaks of CA structures shown in Table 1. This indicated that there was shifting peaks of bacterial cellulose (BC) to bacterial

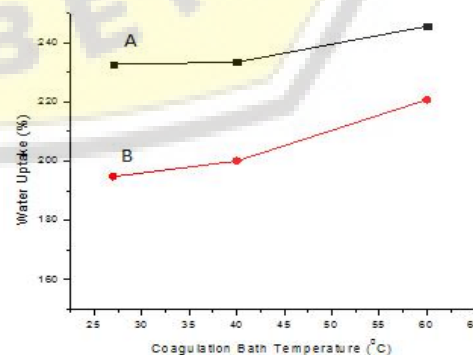


Figure 4. Water uptake (%) of the blend membranes, with (A) PSF/CCA and (B) PSF/CA

Cellulose acetate with its acetyl groups had high affinity to water. Adding PEG-400 to the system influence pore formation of the membranes. In the water uptake analysis, the hydrophilicity of the blend membranes greater than PSF membrane more than 10 times. Low interaction between water and PSF was possible due to high hydrophobicity of PSF. However, adding hydrophilic functional groups from CA increased interaction with water. This interaction occurred not only at the membrane surfaces, but also penetrated into pore, which formed PEG-400. The interaction water with hydrophilic functional groups in surface and pore was the major reason for high percentage water uptake of the blend membranes than PSF one.

The influence of coagulation bath temperature on water flux showed good agreement with %water uptake analysis. Figure 5 indicates the changes of water flux to the coagulation bath temperature. Variation in coagulation bath temperature (CBT) showed an increase in both water uptake and water flux from room temperature (27 °C) to 60 °C.

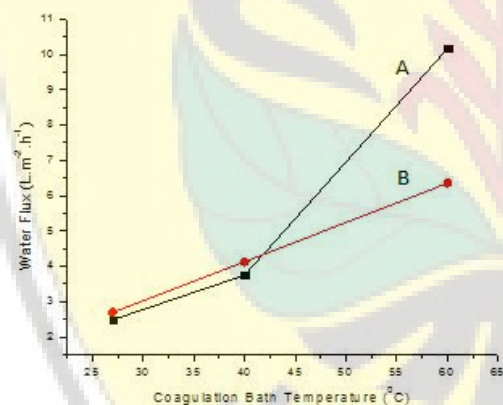


Figure 5. Water Flux of blend membranes, with (A) PSF/CCA and (B) PSF/CA

CBT plays an important role in membrane formation. Room temperature (27 °C) created a normal condition for solvent-nonsolvent exchange. The hydrophilic-hydrophobic interaction between CA-PSF and the presence of PEG enhanced the viscosity of dope solutions, thus introduce to delayed demixing

(Manawi, *et al.*, 2017), and produced denser skin layers, low porosity and lower water flux.

Rate of membrane formation affect the membrane structure. In demixing process, nuclei were growth and continue occur by solvent- non solvent exchange (Sanmugamet *et al.*, 2017). The mobility of the solvent and non-solvent exchange was enhanced by increased temperature, leading to a more rapid precipitation and producing a thinner skin layer of the membranes (Peng *et al.*, 2010). When casting solution immersed into coagulation bath with higher CBT, the solvent move quickly out and the non solvent enters into the polymer. Nucleation occurs faster on the skin layer and retard the solvent in the sub layer to come out. It was prevent nucleation on sub layer (Farahani *et al.*, 2016). This phenomenon introduce the polymer to have macrovoids structure on sub layer. Formation of macrovoids generally happens on quick precipitation process and precipitation is faster at higher temperature (Saljoughi *et al.*, 2010). For that reason, higher CBT produce thinner skin layer, more macrovoids, and higher porosity, thus increasing water flux.

Porosity of PSF/CA was found smaller than PSF/CCA blend membranes, showed by Figure 6. Mean pore radius was calculated for the blend membrane, and show variation of pore radius from 50 nm to 180 nm with different CBT (Table 2).

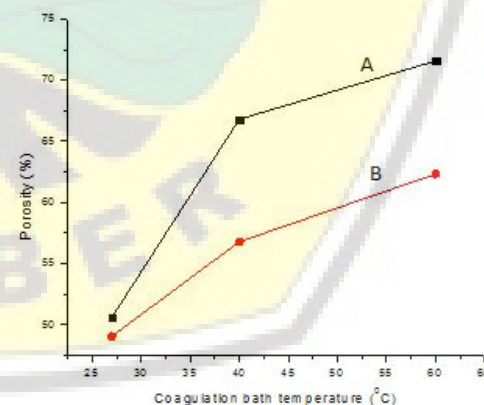


Figure 6. Porosity of blend membranes, with (A) PSF/CCA and (B) PSF/CA.



Table 2. Mean Pore Radius of Blend Membrane

Temperature of Coagulation Bath (CBT) (°C)	Blend Membran PSF/CA (nm)	Blend Membran PSF/CCA (nm)
27	71.6	46.6
40	99.2	92.3
60	101.1	119.4

*Thermal Properties*

Table 3. Transition Glass (Tg) and Melting Temperature (Tm) of Blend Membrane

Membranes*	Tg (°C)	Tm (°C)
PSF/CCA 27 °C	137	219
PSF/CA 27°C	175	231
PSF/CA 40°C	195	264
PSF/CA 60°C	194	278

\*with different CBT

The analysis of the thermal properties of blend membranes using Differential Scanning Calorimetry gave information on blending properties and flexibility of the membranes. Single transition glass temperature (Tg) was found. This showed that the blending of the membranes were homogenous. An increase in Tg indicated that the flexibility of membranes decreased. It contributed to aggregation and contraction of polymer chains during the formation of the blend membranes in the coagulation bath (Saljoughi *et al*, 2010). Rapid movement of water as non solvent due to higher temperature and low miscibility between water and polymers in blend membran resulted in restriction in rotation molecules, thus increasing Tg. Table 3 show Tg and Tm data of the membranes. On another hand, the melting point (Tm) of the membranes showed a good agreement with water uptake and water flux.

**CONCLUSION**

Blend membranes PSF/CA that come from bacterial cellulose have been successfully prepared. The different CBT lead to the different properties of blends membrane, include water uptake, water flux and porosity. With increase temperature in coagulation bath increased water uptake, water flux and porosity. Compare with membrane PSF/CCA, the blend membranes PSF/CA have lower in water uptake, water flux and porosity for all CBT. However, blend membrane based CA from bacterial cellulose have similar properties with membrane based CA from commercial

one (CCA). Thermal analysis showed single transition glass temperature indicating homogeneity of the PSF/CA blend membrane. Hence, controlling in CBT would help to membranes structure formation.

**REFERENCES**

- Ahmad, A., Waheed, S., Khan, S. M., E-Gul, S., Shafiq, M., Farooq, M., Sanauallah, K., Jamil, T. 2015. Effect of the Silica on the Properties of Cellulose Acetate/Polyethylene Glycol Membranes for Reverse Osmosis. *Desalination*, 355 : 1-10.
- Farahani, M.H.D.A., Rabiee, H., Vatanpour, V., Borghei, S.M. 2016. Fouling Reduction of emulsion polyvinylchloride ultrafiltration membrane blended by PEG: the effect of additive concentration and coagulation bath temperature. *Desalination and Water Treatment*, 57:26, 11931-11944. DOI:10.1080/19443994.2015.1048739.
- Fei, Z., Huang, S., Yin, J., Xu, F., Zhang, Y. 2015. Preparation and Characterization of Bio-Based Degradable Plastic Film Composed of Cellulose Acetate and Starch Acetate. *J. Polym. Environ.* (2): 383-391.
- Golpour, M., Pakizeh, M. 2017. Development of a new nanofiltration membrane for removal kinetic hydrate inhibitor from water. *J. Seppur*. 183: 237-248.
- Halib, N., Amin, M.C.I.M., Ahmad, I. 2012. Physicochemical Properties and Characterization of *Nata de Coco* from Local Food Industries as a Source of Cellulose. *Sains Malaysiana* 41(2): 205-211.

- Holda, A.K., Aernouts,B., Saeys, W., Vankelecom, I.F.J. 2013. Study of Polymer Concentration and Evaporation Time as Phase Inversion Parameters for Polysulfone-based SNRF Membranes. *J. Mem. Sci.*442 : 196-205.
- Liu, C., Mao, H., Zhu, J., Zhang, S. 2017. Ultrafiltration Membrane with Tunable Morphology and Performance Prepared by Blending Quaternized Cardo(Poly-Arylene Ether Sulfone)s Ionomers with Polysulfone. *J.Sepur.*179 : 215-224.
- Mahdavi, H., and Shahalizade,T. 2015. Preparation, Characterization, and Performance Study of Cellulose Acetate Membranes Modified by Aliphatic Hyperbranch Polyester. *J.Mem. Sci.* 473: 256-266.
- Manawi, Y., Kochkodan, V., Mohammad, A.W., Atieh, M.A. 2017. arabic gum as a novel pore-forming and hydrophilic agent in polysulfone membrane. *J.memsci.* 529 : 95-104.
- Mansourizadeh, A., and Asad, A.J. 2014. Preparation of Blend Polyethersulfone/Cellulose Acetate/Polyethylene Glycol Asymmetric Membranes for Oil-Water Separation. *J. Polym. Res.*, 21 : 375.
- Nedjma,S., Djidjelli, H., Boukerrou, A., Benachour, D., Chibani, N. 2012. Deinked and Acetylated Fiber of Newspaper. *J. Appl. Polym. Sci.*, 127 :4795-4801.
- Pang, B., Li, Q., Tang, Y., Zhou, B., Liu, T., Lin,Y. and Wang, X. 2015, Fabrication of cellulose acetate ultrafiltration membrane with diphenyl ketone via thermally induced phase separation. *J. Appl. Polym. Sci.*, 132, 42669, doi: 10.1002/app.42669
- Peng, J., Su, Y., Chen, W., Shi, Q., Jiang, Z. 2010. Effect of Coagulation Bath Temperature on the Separation Performance and Antifouling Property of Poly(ether sulfone) Ultrafiltration Membranes. *Ind. Eng. Chem. Res.*, 49 : 4858-4864.
- Radiman, C., and Yuliani, G. 2008. Coconut Water as a Potential Resource for Cellulose Acetate Membrane Preparation. *Polym. Int.*, 52 : 502-508.
- Richards,H.L., Baker, P.G.L., Iwuoha, E. 2012. Metal Nanoparticles Modified Polysulfone Membranes for use in Wastewater Treatment : A Critical Review. *J.SEMAT.*, 2 : 183-193.
- Saljoughi, E., Amirilargani, M., Mohammadi, T. 2010. Effect of PEG Additive and Coagulation Bath Temperature on the Morphology, Permeability and Thermal/Chemical Stability of Asymmetric CA Membranes. *Desalination*, 262 : 72-78.
- Sanmugam, S., Harruddin, N., Saufi, S.M. 2017. Effect of Coagulation Bath Temperature during Preparation of PES Hollow Fiber Supported Liquid Membrane for Acetic Acid Removal. *Chem. Eng. Res. Bull.*, 19:118-122.
- Shivakumar, M., Susithra, L., Mohan, D.R., Rangarajan, R. 2006. Preparation and Performance of Polysulfone-Cellulose Acetate Blend Ultrafiltration Membrane. *J. Macromol. Sci.*, 43:1541-1551.
- Zhong, L., Ding, Z., Li, B., Zhang, L. 2015 . Preparation and Characterization of Polysulfone/Sulfonated Polysulfone/Cellulose Nanofiber Ternary Blend Membranes. *BioResources*, 10(2) : 2936-2948.
- Zodrow, K., Brunet, L., Mahendra, S., Li, D., Zhang, A., Li, Q., Alvarez, P.J.J. 2009. Polysulfone Ultrafiltration Membranes Impregnated with Silver Nanoparticles Show Improved Biofouling Resistance and Virus Removal. *J. Wat. Res.*, 43:715-723.

